

i+s p45-17

**SYNTHESIS AND ELECTRICAL CHARACTERIZATION OF
LI (Ni_{1/3}Co_{1/3-x}Mn_{1/3}M_x)O₂, (M=Fe, Al, Mg, Cu AND X=0.04, 0.08) FOR THE
CATHODE OF LI-ION RECHARGEABLE BATTERIES**

S.W.M.P.W.A.N.B Weerakoon¹, T.H.N.G Amaraweera² and H.W.M.A.C Wijayasinghe²

¹*Department of Physics, The Open University of Sri Lanka,*

²*Institute of Fundamental Studies, Hantana Road, Kandy*

INTRODUCTION

Energy can be stored in many forms, among which batteries are the most versatile energy storing method to be used in almost all portable devices, where a power source is required. When we consider popular rechargeable batteries, the Li-ion battery (LIB) has twice the specific energy compared to Ni metal hydride battery and four times that of Ni-Cd battery.

In searching for alternative cathode materials to replace the costly LiCoO₂ in LIB, the layer structured NMC compositions, which contains the transition metal elements of Ni, Mn and Co, such as Li (Ni_yCo_{1-2y}Mn_y)O₂ system has extensively been studied. Li(Ni_{1/3}Co_{1/3}Mn_{1/3})O₂ is an important member of this system (Whittingham, 2004). The electrochemical performances and safety of these materials are analogous or even superior to that of LiCoO₂ (Xu, 2012).

Further development of this Li (Ni_{1/3}Co_{1/3}Mn_{1/3})O₂ system by substituting Co by other cheaper metal oxides, Li(Ni_{1/3}Co_{1/3x}Mn_{1/3}M_x)O₂, (M=Fe, Al, Mg, Cu and x = 0.11, 0.22, 0.33), has recently been investigated by this group (Samarasingha, 2013). The outcome of it indicated the importance of studying the lower level substitutions (x < 0.11). Therefore this work was based on investigations of (Ni_{1/3}Co_{1/3x}Mn_{1/3}M_x)O₂ (M=Fe, Al, Mg, Cu and x= 0.04 and 0.08) synthesized by the Pechini method. This is a low cost synthesis technique but can result in powders with high purity, homogeneity and particle morphology (Wijayasinghe, 2006) that are greatly preferred for the rechargeable Li-ion battery cathodes.

METHODOLOGY

Li(Ni_{1/3}Co_{1/3x}Mn_{1/3}M_x)O₂, (M=Fe, Al, Mg, Cu and x= 0.04 and 0.08) powders were synthesized using Pechini method. In this, stoichiometric amount of metal Nitrates, LiNO₃, Ni(NO₃)₂.6H₂O, Co(NO₃)₂.6H₂O, Mn(NO₃)₂.4H₂O, Fe(NO₃)₃.9H₂O, Al(NO₃)₃.9H₂O, Mg(NO₃)₂.6H₂O, Cu(NO₃)₂.3H₂O of analysis grade were used as starting materials with the organic precursor solutions of citric acid (CA) and ethylene glycol (EG). Powders were prepared with the EG/CA ratio of 4:1, because the previous studies have proved that optimal gelling condition occur at this ratio (Samarasingha *et al.*, 2008). The mixture of nitrates, citric acid, and ethylene glycol was stirred for 20 hours and then heated while being stirred (Samarasingha *et al.*, 2013). The resultant powders were calcined at 900 °C in air in a box furnace. The phase analysis was carried out with X-ray diffractometry (XRD, Siemens D5000 using monochromatic Cu K α radiation). The calcined powders were pressed in to green pellets of 12 mm in diameter, followed by sintering at 1000 °C in a box furnace in static air. The d.c. electrical conductivity measurements were performed on gold pasted sintered pellets, on heating and cooling in the temperature range between room temperature (25°C) and 200°C.

¹Correspondences should be addressed to S.W.M.P.W.A.N.B Weerakoon, ¹Department of Physics, The Open University of Sri Lanka (email: nuwanweerakoon87@gmail.com)

significantly increased conductivity. As a whole, this study reveals the possibility of synthesizing these materials by Pechini method with appropriate phase purity and considerable electrical conductivity for the LIB cathode application.

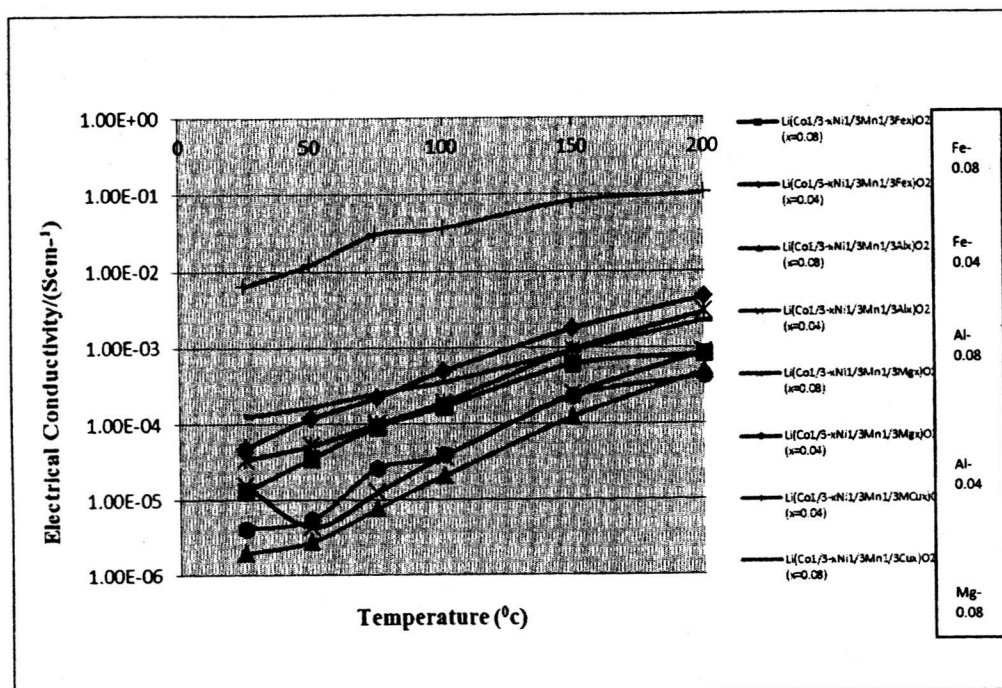


Figure 2: Variation of the d. c. electrical conductivity of synthesized powders with temperature.

Table 1: The d.c. electrical conductivity of synthesized powders at room temperature (25 °C)

| Composition of synthesized powders | X (mole %) | DC electrical conductivity(S/cm) at room temperature (25°C) |
|--|------------|---|
| Li (Ni _{1/3} Co _(1/3-x) Mn _{1/3})O ₂ (The base material) | 0.00 | 7.85 x 10 ⁻⁰⁵ |
| Li (Ni _{1/3} Co _(1/3-x) Mn _{1/3} Fe _x)O ₂ | 0.08 | 1.31 x 10 ⁻⁰⁵ |
| | 0.04 | 4.88 x 10 ⁻⁰⁵ |
| Li (Ni _{1/3} Co _(1/3-x) Mn _{1/3} Al _x)O ₂ | 0.08 | 1.98 x 10 ⁻⁰⁶ |
| | 0.04 | 1.58 x 10 ⁻⁰⁵ |
| Li (Ni _{1/3} Co _(1/3-x) Mn _{1/3} Mg _x)O ₂ | 0.08 | 3.43 x 10 ⁻⁰⁵ |
| | 0.04 | 4.20 x 10 ⁻⁰⁶ |
| Li (Ni _{1/3} Co _(1/3-x) Mn _{1/3} Cu _x)O ₂ | 0.08 | 1.26 x 10 ⁻⁰⁴ |
| | 0.04 | 6.36 x 10 ⁻⁰³ |

CONCLUSIONS

The XRD phase analysis performed on Li (Ni_{1/3}Co_(1/3-x)Mn_{1/3}M_x)O₂ (M=Fe,Al,Mg,Cu),(x=0.04,0.08) materials prepared by the Pechini method in this study, revealed the formation of only the appropriate layered R3m structure in all the synthesized and caicined at 900 °C.

The measured conductivity at 25 °C is varies according to the material composition. The Cu substituted materials show the highest electrical conductivity, which was $6.36 \times 10^{-03} \text{ Scm}^{-1}$ at room temperature. Accordingly, this study shows the possibility of synthesizing $\text{Li}(\text{Ni}_{1/3}\text{Co}_{(1/3-x)}\text{Mn}_{1/3}\text{M}_x)\text{O}_2$ ($\text{M}=\text{Fe,Al,Mg,Cu}$) materials by the Pechini method with appropriate phase purity and electrical conductivity for the LIB cathode application.

REFERENCES

- Scherson, D.A., and Palencsar, A. (2006). *Interface*, The Electrochemical Society. : 1519.
- Samarasingha, P., Diem-Hang Tran-Nguyen, Marten Behm and Athula Wijayasinghe, (2008). *Electrochim. Acta.* 53:7995.
- Pushpaka Samarasinghe, Athula Wijayasinghe, Morten Behm, Lakshman Dissanayake and Goran Lindberg. (2013). Synthesis and electrical characterization of Fe and Al doped $\text{Li}(\text{Ni}_{1/3}\text{Co}_{1/3}\text{Mn}_{1/3})\text{O}_2$ for Lithium ion rechargeable battery cathodes, submitted to *Solid State Ionics*.
- Wijayasinghe A., Bergman B. and Lagergren C. (2006). *Solid State Ionics* : 177.
- Whittingham, S., (2004) : *Chemical Review* 104:287.

ACKNOWLEDGMENTS

Mr. W.G. Jayasekara of the Institute of Fundamental Studies, Kandy Sri Lanka and Mr. P. Samarasingha of the Department of Chemistry, University of Oslo, Norway are kindly acknowledged for their support during this work.